arXiv:cond-mat/0510312v3 [cond-mat.str-el] 29 Mar 2006

Lightly doped La$_{2-x}$Sr$_x$CuO$_4$ as a Lifshitz helimagnet

V. Juricic,[1] M. B. Silva Neto,[1] and C. Morais Smith[1]

[1] *Institute for Theoretical Physics, University of Utrecht,*
Leuvenlaan 4, 3584 CE Utrecht, The Netherlands.

We study the static magnetic correlations in lightly doped La$_{2-x}$Sr$_x$CuO$_4$ within the framework of a dipolar frustration model for a canted antiferromagnet. We show that the stability of the canted Néel state for $x < 2\%$ is due to the Dzyaloshinskii-Moriya and XY anisotropies. For higher doping the ground state is unstable towards a *helicoidal* magnetic phase where the transverse components of the staggered magnetization rotate in a plane perpendicular to the orthorhombic b-axis. Our theory reconciles, for the first time, the incommensurate peaks observed in elastic neutron scattering with Raman and magnetic susceptibility experiments in La$_{2-x}$Sr$_x$CuO$_4$.

PACS numbers: 74.25.Ha, 75.10.Jm, 74.72.Dn

Introduction.– The magnetic and transport properties of La$_{2-x}$Sr$_x$CuO$_4$ (LSCO) evolve tremendously with doping [1]. For $0 < x < x_{AF} \simeq 0.02$, LSCO is a Mott-Hubbard insulator that exhibits 3D antiferromagnetic (AF) order with a Néel temperature $T_N \simeq 325$K at $x = 0$. For $x_{AF} < x < x_{SC} \simeq 0.055$, inside the spin-glass (SG) phase, static incommensurate (IC) magnetic correlations are observed in neutron scattering, demonstrating the importance and persistence of the strong AF correlations well after the Néel long range order has been destroyed. Further doping, $x > x_{SC}$, eventually drives the system into a superconducting (SC) state, where dynamic magnetic correlations are also known to play an important role [1].

Inelastic neutron scattering (INS) experiments within the SC phase have revealed that dynamical IC spin correlations coexist with superconductivity [2]. Moreover, the experimentally observed four peaks associated with the IC magnetic order are accompanied by charge peaks, with periodicity twice the magnetic one, provided a low-temperature tetragonal phase is stabilized (as, for example, by Nd doping) [3]. These features have been consistently interpreted within a model of stripes acting as antiphase domain walls [4]. More recently, static IC magnetic correlations have also been observed within the low-temperature orthorhombic (LTO) SG phase of LSCO [5]. In this case, only two IC peaks, rotated by 45° with respect to the ones in the SC phase, have been observed. Because such incommensurability follows the same linear dependence upon doping as the other four peaks [6], the above results, as well as recent Raman measurements [7], have been interpreted as a signature of diagonal stripe order. However, associated charge peaks have never been observed in the LTO phase of LSCO, what raises the question of the validity of the diagonal stripe picture within the insulating SG phase.

Recently, a model based on the seminal ideas of Shraiman and Siggia [8] has been proposed. It accounts for the observed magnetic IC diagonal peaks without having to assume a charge order [9]. Within this model, the two IC magnetic peaks would originate from a spiral state, with the staggered magnetization rotating within the CuO$_2$ layers (ab plane), in such a way that the measured magnetic incommensurability would correspond to the inverse spiral pitch. More recently, Sushkov and Kotov have considered a similar spiral state in the $t-t'-t''-J$ model [10]. It was shown that while in the insulating region, $x < x_{SC}$, the diagonal $(1,1)$ and $(1,-1)$ spirals have lower energy than the horizontal $(1,0)$ and vertical $(0,1)$ ones due to the Coulomb trapping of the doped hole near the Sr ion, in the metallic state, $x > x_{SC}$, the Fermi motion energy favors the $(1,0)$ and $(0,1)$ spiral states, leading to a jump of 45° in the direction of the spiral pitch across the metal-insulator transition.

Despite being able to qualitatively explain neutron scattering data in the SG phase, the above spiral pictures have two major problems: i) the collinear Néel state is unstable towards the spiral state already at infinitesimal doping, $x \neq 0$; ii) the spiraling of the staggered magnetization in the CuO$_2$ layers is not consistent with magnetic susceptibility experiments in LSCO, which indicate that the Cu^{++} spins remain confined to the bc plane throughout the SG phase (χ_a remains featureless) [11]. In this Letter we demonstrate that only by considering properly both the Dzyaloshinskii-Moriya (DM) and XY anisotropies the above two problems can be solved, and we provide an elegant description of the unified physics of IC correlations and anisotropic magnetic response in the SG phase of LSCO. We show that the anisotropies give *robustness* to the *canted* Néel state for $x < x_{AF}$ and that the same anisotropies lead to the formation of a *Lifshitz helimagnet* above x_{AF}, with the small transverse components of the staggered magnetization rotating in the ac plane. Such helix rotation of the staggered magnetization is accompanied by a small precession of the *local* magnetization (weak-ferromagnetic (WF) moment) around the out-of-plane c-axis. The *space integrated* sublattice magnetization and WF moment, on the other hand, are oriented along the b- and c-axis, respectively, in such a way that, from the point of view of the magnetic susceptibility, the total spin is confined to the bc plane, in agreement with experiments [11].

The model.– The presence of static magnetic correlations within the SG phase of LSCO allows us to use a Hamiltonian description of the long-wavelength fluctuations of the *staggered* order parameter, $\mathbf{n}$ (see [12, 13] for a detailed derivation of the model). For $x = 0$ we can write (we use a soft version of the $\mathbf{n}^2 = 1$ constraint)

$$\mathcal{H}_M = \frac{1}{2t}\int d^2\mathbf{x}\left\{(\nabla\mathbf{n})^2 + \frac{1}{2}\left(\frac{m_\alpha}{Ja}\right)^2 n_\alpha^2 + \frac{u_0}{2}(\mathbf{n}^2-1)^2\right\}, \tag{1}$$

where $\mathbf{n}$ is the local staggered magnetization, $t^{-1} \equiv \rho_s/T$ is the renormalized classical spin stiffness, with $\rho_s = JS^2$, J is the AF superexchange, a is the lattice constant, T is the temperature, and $S = 1/2$ is the spin. The effect of both the DM and XY anisotropies is to generate gaped transverse excitations. We define m_α, ($\alpha \equiv a, b, c$), as the bare masses of the magnetic excitations along the three directions of the LTO phase. The bare masses m_a and m_c are related to the DM and XY anisotropy parameters, respectively, whereas the mass of the longitudinal mode, m_b (the heaviest of all three), is proportional to the coupling constant u_0. Furthermore, the *uniform* part of the Cu^{++} spins, $\mathbf{L}$, is related to the staggered order parameter, $\mathbf{n}$, through $\langle\mathbf{L}\rangle = (1/2)(\langle\mathbf{n}\rangle \times \mathbf{D}_+)$, and gives rise to a WF moment perpendicular to the $\mathrm{CuO_2}$ layer [12, 13]. Here $\mathbf{D}_+ = (D_+, 0, 0)$ is a thermodynamic DM vector oriented along the a-axis, related to the tilting angle of the oxygen octahedra $D_+ \sim \delta$ [13], and we use units such that $J = a = 1$.

The effect of a small number of holes ($x \neq 0$) on an antiferromagnet can be characterized, in a coarse-grained description, in terms of a dipolar frustration of the AF background [8, 9]. We introduce a dipolar field, $\mathbf{P}_\mu$, that couples to the AF magnetization current as

$$\mathcal{H}_{int} = -2\lambda\int d^2\mathbf{x}\,\mathbf{P}_\mu\cdot(\mathbf{n}\times\partial_\mu\mathbf{n}), \tag{2}$$

where $\lambda \equiv \tilde{\lambda}/T$ is the dipolar coupling constant, $\tilde{\lambda} \sim 1$ [14], and the field P_μ^α is a vector in both lattice and spin spaces. The above mathematical form belongs to a class known as *Lifshitz invariants*, which play an important role in stabilizing long-period spatially modulated structures with fixed sense of rotation of the vectors $\mathbf{n}$ in systems like $\mathrm{Ba_2CuGe_2O_7}$ and $\mathrm{K_2V_3O_8}$ [15].

In the case of a nonuniform configuration for the dipolar field, $\mathbf{P}_\mu$, we can write

$$\mathcal{H}_D = \frac{1}{2\kappa}\int d^2\mathbf{x}\left\{(\nabla\mathbf{P}_\mu)^2 + \mu_{\alpha\mu}^2(P_\mu^\alpha)^2\right\}, \tag{3}$$

where $\kappa = \tilde{\kappa}T$ with $\tilde{\kappa}$ denoting the dipole stiffness, and $\mu_{\alpha\mu}$ is the bare mass of the dipole field, P_μ^α, which, in microscopic terms, is related to the energy cost of populating the μth valley of the vacancy Fermi surface with the spin polarization α [8, 14].

The appearance of elastic IC peaks in neutron scattering can occur, in principle, whenever $\langle\mathbf{P}_\mu\rangle \neq 0$. We thus calculate the effect of the magnons on the self-energy of the dipolar fields, arising from the dipole-magnon interaction in Eq. (2). Straightforward calculations yield

$$\begin{aligned}\mathcal{M}_{\alpha\mu}^2 &= \mu_{\alpha\mu}^2 - 8\kappa(t\lambda)^2\epsilon_{\alpha\beta\gamma}\epsilon_{\alpha\beta\gamma}\\ &\times\int\frac{d^2\mathbf{k}}{(2\pi)^2}\frac{k_\mu k_\mu}{(k^2+m_\beta^2/2)(k^2+m_\gamma^2/2)}.\end{aligned} \tag{4}$$

The Fermi wavevector $k_F = \sqrt{\pi x}$ provides the cutoff in the momentum integrals, because the coarse-grained description employed here is valid on length scales much larger than the distance between the holes, $l \gg k_F^{-1} \sim x^{-1/2}$ [8, 14]. Inspection of Eq. (4) reveals that, even when the bare dipole masses are isotropic in the spin space, $\mu_{\alpha\mu} \equiv \mu_\mu$, $\forall\alpha$, the renormalized ones may be anisotropic due to the dipolar interaction, Eq. (2), which involves different magnon modes. Moreover, an instability to a phase with $\langle P_\mu^\alpha\rangle \neq 0$ may indeed occur. In particular, when $m_a = m_c = 0$, such instability appears already at infinitesimal doping, because the momentum integral in Eq. (4) diverges logarithmically. Finally, due to the hierarchy between the masses of the magnon modes, $m_a < m_c \ll m_b$ (actually $m_b \to \infty$ in the nonlinear $\mathbf{n}^2 = 1$ description), we find that $\mathcal{M}_{\alpha\mu}^2$ will become negative first for the spin component of the dipolar field along the orthorhombic b-axis.

Canted Néel state.– Let us consider first the low doping regime where $\langle P_\mu^\alpha\rangle = 0$. In this case, the magnetism is commensurate and the fluctuating dipoles give rise to corrections to the magnon self-energy in one-loop approximation. The renormalized propagator for the n_α field reads $G_{\alpha\beta}(\mathbf{q}) = t\delta_{\alpha\beta}(q^2 + m_\alpha^2/2 - \Sigma_\alpha(\mathbf{q}))^{-1}$, where $(\alpha \neq \beta \neq \gamma)$

$$\begin{aligned}\Sigma_\alpha(\mathbf{q}) &= \kappa(t\lambda)^2\epsilon_{\alpha\beta\gamma}\epsilon_{\alpha\beta\gamma}\\ &\times\int\frac{d^2\mathbf{k}}{(2\pi)^2}\frac{(k+q)_\mu(k+q)_\mu}{(k^2+m_\beta^2/2)[(\mathbf{k}-\mathbf{q})^2+\mu_{\gamma\mu}^2]}.\end{aligned}$$

The above self-energy is an analytical function of the momentum and thus we write $\Sigma_\alpha(\mathbf{q}) = \Sigma_\alpha(0) + (1/2)q_\mu q_\nu\partial^2\Sigma_\alpha(\mathbf{q})/\partial q_\mu\partial q_\nu|_{\mathbf{q}=0}$. The first term in the self-energy, $\Sigma_\alpha(0)$, gives rise to corrections to the magnon mass

$$\begin{aligned}M_\alpha^2 &= m_\alpha^2 - 2\kappa(t\lambda)^2\epsilon_{\alpha\beta\gamma}\epsilon_{\alpha\beta\gamma}\\ &\times\int\frac{d^2\mathbf{k}}{(2\pi)^2}\frac{k_\mu k_\mu}{(k^2+m_\beta^2/2)(k^2+\mu_{\gamma\mu}^2)},\end{aligned} \tag{5}$$

whereas the second term leads to a reduction of the spin stiffness,

$$\begin{aligned}\tilde{\rho}_{s\mu\nu} &= \rho_s\delta_{\mu\nu} - \delta_{\mu\nu}\kappa(t\lambda)^2\epsilon_{\alpha\beta\gamma}\epsilon_{\alpha\beta\gamma}\\ &\times\int\frac{d^2\mathbf{k}}{(2\pi)^2}\frac{(k^2)^2+\mu_{\gamma\nu}^4}{(k^2+m_\beta^2/2)(k^2+\mu_{\gamma\nu}^2)^3}.\end{aligned} \tag{6}$$

It is clear now from Eqs. (4) and (5) that it is exactly the DM and XY anisotropies that give *robustness* to the canted Néel state at low doping, because they lead to nonvanishing magnon gaps, $m_a \neq 0$ and $m_c \neq 0$. Most remarkably, we find that the reduction of the DM gap, M_a, is consistent with recent Raman scattering experiments by Gozar *et al.* [16], which show that the DM gap decreases with doping and vanishes at $x = x_{AF} \simeq 2\%$, when the SG phase sets in. Experimentally, at $x = 1\%$ the decrease of the DM gap is about 26% [16]. Such huge renormalization, however, *cannot* be explained simply from the decrease of the tilting angle of the oxygen octahedra in the LTO phase of LSCO, which is known to happen with Sr doping. Our model yields the decrease of the DM gap with doping due to the coupling of the background magnetization current to the dipoles, Eq. (2). Using Eq. (5) with the bare values of parameters, $\tilde{\kappa} \sim 1.1$, $\tilde{\lambda} \sim 1$, $t \sim 1/S^2$, $m_a \sim 2.5 \cdot 10^{-2}$, $m_c \sim 5 \cdot 10^{-2}$, and $\mu \sim 1$ [14], we determine the doping dependence of the DM gap, at $T = 10$ K (see Fig. 1). The reduction of the DM gap at $x = 1\%$ is about 27%, in remarkable agreement with the experiments. Moreover, from the vanishing of the DM gap we obtained the critical concentration $x^{th}_{AF} = 0.0198 \simeq 2\%$, as experimentally observed [16], signaling the instability of the Néel phase.

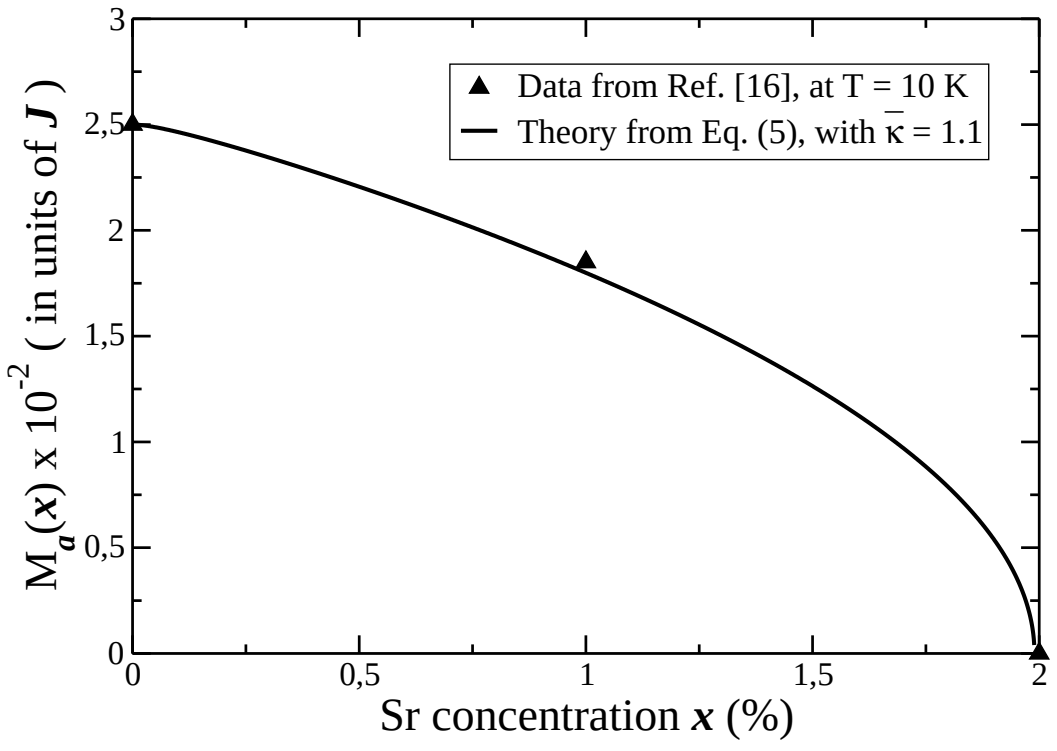

FIG. 1: Doping dependence of the DM gap as given by Eq. (5) using the bare parameters of the model. Experimental data from Ref. [16] taken at $T = 10$ K.

Our results are also consistent with recent magnetic susceptibility measurements [11]. Within our model, the only effect of doping is the reduction of the magnon masses and of the spin stiffness (see Eqs. (5) and (6)). Therefore, we expect the qualitative features of the susceptibility in the AF region of LSCO to remain the same as in the undoped compound [13]. The peaks in both χ_b and χ_c susceptibilities will be shifted towards lower temperatures, because both the reduction of the magnon gaps and of the stiffness with doping lead to a decrease of the Néel temperature, T_N. This is indeed observed experimentally [11]. Furthermore, we find that the unusual $T = 0$ hierarchy of the susceptibilities, $\chi_a < \chi_c < \chi_b$, is preserved [13] (once the anisotropic van Vleck contribution to χ_c is subtracted [11]) with $\chi_a \approx \sigma_0^2/t$, $\chi_b = (1/t)(D_+^2/M_c^2(x))$, and $\chi_c \approx \chi_a + (1/t)(D_+^2/M_b^2(x))$, where σ_0 measures the Cu^{++} effective moment [13].

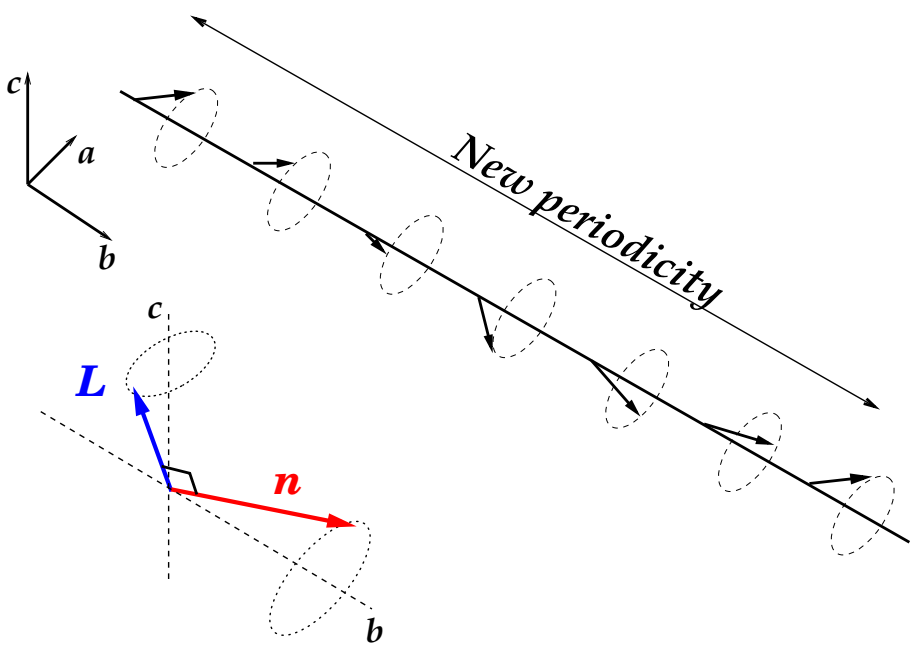

FIG. 2: (Color online) Helix rotation of the staggered magnetization for $x > x_{AF}$. Notice that the longitudinal component is the largest, and the small transverse ones describe an ellipse in the ac plane.

Helicoidal state.– Let us consider now the case of higher doping where an instability towards a phase with $\langle P^\alpha_\mu \rangle \neq 0$ may occur. The easy axis for the spin part of the dipolar field is the orthorhombic b-axis, which is a consequence of the hierarchy $m_a < m_c \ll m_b$. As the lattice part is concerned, our model is isotropic, and, as such, cannot determine the lattice direction of the dipolar field. Motivated by neutron scattering experiments, we assume that the dipolar field acquires the expectation value along the b-axis in the lattice space. In order to obtain the corresponding nonuniform configuration for the staggered order parameter we consider $\langle \mathbf{P}_\mu \rangle = (0, P_0, 0)\delta_{\mu b}$, and solve the equations of motion for the $\mathbf{n}$ fields. The resulting local staggered magnetization reads

$$\mathbf{n}(\mathbf{x}) = (\sigma_a \cos(\mathbf{Q} \cdot \mathbf{x}),\ \sigma_b,\ \sigma_c \sin(\mathbf{Q} \cdot \mathbf{x})), \tag{7}$$

with $\sigma_c = -\sigma_a (Q^2 + m_a^2)/\tilde{P}_0 Q$ and

$$2Q^2 = \tilde{P}_0^2 - m_a^2 - m_c^2 + \sqrt{(\tilde{P}_0^2 - m_a^2 - m_c^2)^2 - 4m_a^2 m_c^2}, \tag{8}$$

for $\tilde{P}_0^2 > m_a^2 + m_c^2$, where $\tilde{P}_0 \equiv -\rho_s \tilde{\lambda} P_0$. The equation of motion for the longitudinal component yields $n_b^2 = 1 - n_a^2 - n_c^2$, and that determines σ_b. The static configuration for the staggered order parameter is nonuniform and its transverse components, n_a and n_c, rotate in a plane perpendicular to the b direction. Therefore the staggered order parameter becomes *helicoidal*, as shown in Fig. 2. Such a magnetic texture arises as a result of the competition between the anisotropies, m_a and m_c, which favor the staggered magnetization along the b-axis, and $\langle P^\alpha_\mu \rangle$, which supports a rotation of the $\mathbf{n}$ field in the ac plane. Since $\langle P^\alpha_\mu \rangle \sim x$ is small, the resulting spin configuration has small components in the ac plane, as shown in Fig. 2.

The local magnetization will precess around the c-axis, see Fig. 2, because $\langle \mathbf{L}(\mathbf{x})\rangle = (1/2)\left(\langle \mathbf{n}(\mathbf{x})\rangle \times \mathbf{D}_+\right)$, but the *total space integrated* magnetization, which is measured by magnetic susceptibility measurements, is still along the c-axis

$$\mathbf{M} = \frac{1}{V}\int \mathrm{d}^2\mathbf{x}\langle \mathbf{L}(\mathbf{x})\rangle = (0, 0, \frac{\sigma_b D_+}{2}),$$

with $\sigma_b^2 = 1 - \sigma_a^2/2 - \sigma_c^2/2$. Since the magnetic susceptibility is obtained from the *total* magnetization, $\mathbf{M}$, we conclude that the nonuniform configuration in Eq. (7) is consistent with the experiments of Lavrov *et al.* [11], which indicate that the Cu^{++} spins remain confined to the orthorhombic bc plane throughout the SG phase, thus yielding a featureless χ_a [11].

The new helicoidal magnetic structure gives rise to IC peaks in neutron scattering at wave vector $\mathbf{Q} = (0, Q, 0)$, corresponding to the inverse helix pitch. Assuming that in the SG phase Eq. (8) holds with renormalized magnon gaps, M_a and M_c, we obtain $Q^2 = \tilde{P}_0^2 - M_c^2 \sim x^2 - M_c^2$, because $M_a(x > x_{AF}) = 0$. This expression allows us to understand both the linear dependence of the incommensurability at higher doping x, when M_c is negligible, as well as a possible deviation from linearity in a region of sizable M_c ($x \rightarrow x_{AF}$). In fact, neutron scattering experiments do exhibit such deviation from linearity at $x = 0.024$ [6].

We can now make an important new theoretical prediction about the behavior of the IC peaks in the presence of an applied magnetic field $\mathbf{B} \perp$ to the CuO$_2$ planes. Since in this case the XY gap softens [12], the incommensurability is expected to reapproach the linear behavior, $Q \sim x$, and is thus larger than for the zero field case. In the stripe picture, on the other hand, the peak positions remain unchanged [17] and thus a perpendicular magnetic field can be used in order to decide between these two scenarios.

Finally, we provide an independent estimate for the critical doping concentration x_{AF}^{th} at which such helicoidal instability takes place, from the behavior of the dipolar mass $\mathcal{M}_{bb}$ at $T = 0$. Assuming that $\mathcal{M}_{bb}$ vanishes at x_{AF}^{th} we find (recall that $k_F = k_F(x)$)

$$\begin{aligned}\mu_{bb}^2 &= \tilde{\kappa}\left(\frac{\tilde{\lambda}}{\rho_s}\right)^2 \frac{M_c}{3\pi}\left(\frac{ck_F}{M_c}\right)^3 \left\{1 - \left[1 - 2\left(\frac{M_c}{ck_F}\right)^2\right]\right. \\ &\times \left.\sqrt{1 + \left(\frac{M_c}{ck_F}\right)^2 - 2\left(\frac{M_c}{ck_F}\right)^3}\right\}. \qquad (9)\end{aligned}$$

In order to estimate x_{AF}^{th} we use the bare value for the mass of the XY mode at the critical point, $m_c \sim 5 \cdot 10^{-2}$, the spin-wave velocity $c = 2S\sqrt{2}$, and for lightly doped LSCO ($x \sim 0.01$), we have $ck_F/M_c \sim 5$, with $k_F = \sqrt{\pi x}$. Thus, in Eq. (9) we can consider M_c/ck_F as a small parameter to obtain $x_{AF}^{th} = \pi(2\mu_{bb}^2\rho_s^2/c\tilde{\kappa}\tilde{\lambda}^2)^2 = 0.0206 \simeq 2.1\%$, since $\tilde{\kappa} \sim 1.1$, $\tilde{\lambda} \sim 1$, $\rho_s \sim S^2$, and $\mu_{bb} \sim 1$ [14], consistent with the vanishing of the DM gap, and in agreement with experiments.

Conclusions.– We propose a description of lightly doped LSCO in terms of a dipolar frustration model of a canted antiferromagnet. For $x < x_{AF}$ the dipole-magnon interaction leads to a reduction of the DM and XY gaps, as well as of the spin stiffness, and the qualitative features of the magnetic susceptibility remain the same as in the undoped compound [13], in agreement with experiments [11]. The robustness of the AF state stems from the DM and XY anisotropies, and for $x_{AF} < x < x_{SC}$ the ground state is unstable towards a helicoidal phase where the local WF moment precesses around the c-axis (see Fig. 2). Such helicoidal magnetic structure gives rise to two IC peaks along the b direction, as observed in neutron scattering [6], while yielding a featureless χ_a [11]. The incommensurability is expected to scale linearly with doping, but to deviate from linearity as $x \rightarrow x_{AF}^+$. We also predict that such linearity is recovered once a perpendicular magnetic field is applied. Our theory provides, for the first time, a consistent description which reconciles neutron scattering, Raman, and magnetic susceptibility measurements in lightly doped LSCO, and inserts the latter into a wider class of Lifshitz helimagnets such as Ba$_2$CuGe$_2$O$_7$ and K$_2$V$_3$O$_8$ [15].

The authors acknowledge invaluable discussions with Y. Ando, L. Benfatto, A. Lavrov, and O. Sushkov.

[1] M. A. Kastner *et al.*, Rev. Mod. Phys. **70**, 897 (1998).
[2] K. Yamada *et al.*, Phys. Rev. B **57**, 6165 (1998).
[3] J. M. Tranquada *et al.*, Nature (London) **375**, 561 (1995).
[4] J. Zaanen and O. Gunnarsson, Phys. Rev. B **40**, 7391 (1989).
[5] S. Wakimoto *et al.*, Phys. Rev. B **60**, R769 (1999); **61**, 3699 (2000); M. Fujita *et al.*, *ibid.* **61**, 3699 (2000); **65**, 064505 (2002).
[6] M. Matsuda *et al.*, Phys. Rev. B **62**, 9148 (2000).
[7] L. Tassini *et al.*, Phys. Rev. Lett. **95**, 117002 (2005).
[8] B. I. Shraiman and E. D. Siggia, Phys. Rev. Lett. **61**, 467 (1988); *ibid* **62**, 1564 (1989).
[9] N. Hasselmann, A. H. Castro Neto, and C. Morais Smith, Phys. Rev. B **69**, 014424 (2004).
[10] O. P. Sushkov and V. K. Kotov, Phys. Rev. B **70**, 024503 (2004); Phys. Rev. Lett. **94**, 097005 (2005).
[11] A. N. Lavrov *et al.*, Phys. Rev. Lett. **87**, 017007 (2001).
[12] J. Chovan and N. Papanicolaou, Eur. Phys. J. B **17**, 581 (2000).
[13] M. B. Silva Neto, L. Benfatto, V. Juricic, and C. Morais Smith, to appear in Phys. Rev. B (2006).
[14] B. I. Shraiman and E. D. Siggia, Phys. Rev. B **46**, 8305 (1992).
[15] A. N. Bogdanov, U. K. Röβler, M. Wolf, and K.-H. Müller, Phys. Rev. B **66**, 214410 (2002).
[16] A. Gozar *et al.*, Phys. Rev. Lett. **93**, 027001 (2004).
[17] B. Lake, *et al.*, Nature **400**, 43 (1999).